

Green synthesis of nano size CoFe_2O_4 using *Chenopodium album* leaf extract for photo degradation of organic pollutants

Fatemeh Mostaghni^{a,*}, Ali Daneshvar^b, Majid Sakhaie^b

Department of Chemistry, Payame Noor University, P.O. BOX 19395-4697 Tehran, Iran

Received: 23 April 2016, Accepted: 17 September 2016, Published: 17 September 2016

Abstract

Green synthesis of nanoparticles makes use of environmental friendly, non-toxic and safe reagents. In this study, we synthesised CoFe_2O_4 in a green approach, using leaf extract of *Chenopodium album*. The structure of the synthesised sample was analyzed by X-ray diffraction methods. The synthesised Photocatalyst was applied for photo degradation of methy orange as a reliable model pollutant. The results indicated that CoFe_2O_4 exhibited good efficiency for the degradation of MO under UV light irradiation; the degradation ratio reached to 100% after 3 h irradiation. In addition, easy separation of the catalysts from the treated wastewater by magnetic separation makes it available for flow-bed technologies.

Keywords: Photo degradation; *Chenopodium album*; magnetic nanoparticles; spinel.

Introduction

Water pollution is one of the important challenges of the world. One of the main causes of disease and mortality in the world is water pollution. Both groundwater and surface water are exposed to various pollutants. Due to different sources of pollutants, natural or man-made, the different classifications for contaminants have been considered. Many contaminants, including a wide variety of organic compounds and metals, are toxic to humans and other organisms. Some of these organic contaminants may be biologically decomposable, but many of them are toxic and not be biologically decomposable. Thus, these compounds can persist in the environment for a long time and will cause harmful effects on humans and ecosystems [1-3].

Therefore, it is necessary to develop the methods in order to be able to degrade the organic contaminants present in the industrial wastewater by an effective, safe and efficient manner.

Among these, the pothocatalytic oxidation using semiconductors can be considered as the most effective technique to remove these contaminants. In recent years, heterogeneous photocatalytic reactions have been actively investigated because of easy separation of the catalysts from the treated wastewater. Among these, spinel ferrite nanoparticles have received much attention in the heterogeneous photo degradation of organic contaminants owing to their unique advantages of complete mineralization of organic pollutant [4-8]. Among spinel ferrites, CoFe_2O_4 is especially interesting due to its strong

*Corresponding author: Fatemeh Mostaghni

Tel: +98 (71) 44354061-7, Fax: +98 (71) 44354071

E-mail: mostaghni@yahoo.com

anisotropy, excellent chemical stability, high coercivity, high corrosion resistivity, moderate saturation magnetization, high mechanical hardness and high Curie temperature [9-11]. CoFe_2O_4 , have the inversed spinel structure with general formula $\text{B}[\text{A}_{0.5}\text{B}_{0.5}]_2\text{O}_4$ [12]. The oxygen atoms are cubic close-packed and the A and B ions occupy both tetrahedral and octahedral positions. All A cations and half of the B cations occupy octahedral sites, while the other half of the B cations occupy tetrahedral sites.

Many preparation methods for CoFe_2O_4 nanoparticles have been reported, such as the ball milling, co-precipitation, hydrothermal synthesis, sol-gel, and reaction in a micro-emulsion [13-17].

In recent years, the biosynthesis of nanoparticles by natural sources including plants, fungi, yeast, bacteria, actinomycetes, and etc. have been actively investigated. Biosynthesis of nanoparticles makes use of eco-friendly, non-toxic and safe reagents [18].

The green method for synthesis of nano particles is simple, efficient, cost effective and eco-friendly in comparison to chemical-mediated synthesis [19-23].

Biosynthesis of nanoparticles especially by plants is the most effective process of synthesis at a very affordable cost [24-27].

In this research, we have utilized the leaf extract of *Chenopodium album* for synthesizing CoFe_2O_4 nanoparticles. *Chenopodium album* is a fast-growing weedy annual plant (Figure 1). It is one of the most widely distributed plants in the world [28], tolerant of poor soils, high altitudes, and minimal rainfall. Global warming is just fine with *Chenopodium album*. In higher concentrations of carbon dioxide, it grows almost double in size. A wide variety of chemical constituent's such as aldehyde, alkaloids, proteins, flavonoids, were reported in phytochemical studies from this plant [29,30].



Figure 1. Picture of *Chenopodium album*

Experimental

Materials

All chemicals used in the experiment were analytical grade and were obtained from Merck (Germany).

Cobalt (II) nitrate hexa hydrate $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, 99.0%, and ferric (III) nitrate hexa hydrate $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$, 98.5%, were used as precursors. X-ray diffraction (XRD) patterns in the 2θ

angular range from 20° to 70° were obtained by a Bruker make Diffractometer using Cu K α X-rays of wavelength ($\lambda=1.5406$ Å). The radiation source was a low pressure mercury UV lamp emitting at 254 nm (30 W, UV-C) which was placed above a batch photoreactor for degradation experiments. The solutions were analyzed by a UV-visible spectrophotometer (PG Instruments-T 70) at $\lambda=477$ nm. All glasswares were washed in dilute HNO₃ acid and rinsed thoroughly with distilled water prior to use. pH was adjusted to the required value with 0.1M HCl. The freshly leaves of *Chenopodium album* (Figure 1) were collected from different agriculture farms at Abadeh, Iran. It was thoroughly washed with distilled water to remove all dust and any dirt, cut into small pieces and dried at room temperature.

Preparation of the leaf extract

The fresh leaf extract used for the synthesis prepared from 20 g of dried leaves were cut to small pieces in a 500 mL Erlenmeyer flask containing 50 mL double distilled water and boiled for 5 min and allowed to cool to room temperature. The aqueous extract was filtered with Whatman 1 filter paper.

Synthesis of magnetite nanoparticles

CoFe₂O₄ were prepared by coprecipitation method. In a typical reaction, Co(NO₃)₂. 6H₂O and FeCl₃.6H₂O with the molar ratios 1:2 were dissolved in 100 mL of double distilled water under mild stirring at room temperature. The mixture was then treated through a drop-by-drop addition of 5 mL of the aqueous solution of *Chenopodium album* leaf extract under vigorous stirring. Final pH of the reaction mixture was adjusted to pH=8 and stirring was continued for 1 h at 60

°C. The mixture was allowed to cool down to room temperature. The precipitate was washed several times with double distilled water and filtered. The resulting powder was then dried and calcined at 450 °C for 3 h. The structure of the synthesised sample was analyzed by X-ray diffraction methods.

Photocatalytic activity test

The photocatalytic activity of the catalyst was examined under irradiation of two 30 w high-power mercury lamps at 254 nm (30 W, UV-C) which were placed above a batch photoreactor. 0.05 g of photocatalyst was added to 100 mL methylorange solution (30 ppm) and the mixture was stirred for 30 min to obtain better dispersion and adsorption performance prior to the degradation. The initial solution pH was adjusted to pH=3 by the diluted HCl solution. The starting point of the reaction was defined as the time when the UV light was turned on and H₂O₂ (1 mL) was added to the reaction mixture. After degradation time lasted 3 h, the remaining MO in the sample solution was determined using a UV-visible spectrophotometer at 477 nm, which is the maximum absorbance wavelength of the MO solution.

Results and discussion

The magnetite nanoparticles CoFe₂O₄ were successfully synthesized by this green method using *Chenopodium album* leaf extract. The *Chenopodium album* leaf extract has the ability to act as reducing agent and stabilizer for magnetite nanoparticles. The magnetite nanoparticles were capped by the C=O of carboxylic group in *Chenopodium album* leaf extract. In this process, initially, metallic salts hydrolyzes to form metallic hydroxide and releases H⁺ ions, thereafter, the hydroxide is partially reduced by the leaf extract to

form CoFe_2O_4 -NPs. At the end of the reaction, CoFe_2O_4 nanoparticles were capped and stabilized by protein chain of leaf extract.

X-Ray diffraction studies

X-ray diffraction pattern of synthesized CoFe_2O_4 is presented in Figure 2. Peak details of synthesized CoFe_2O_4 nanoparticles are summarized in Table 1.

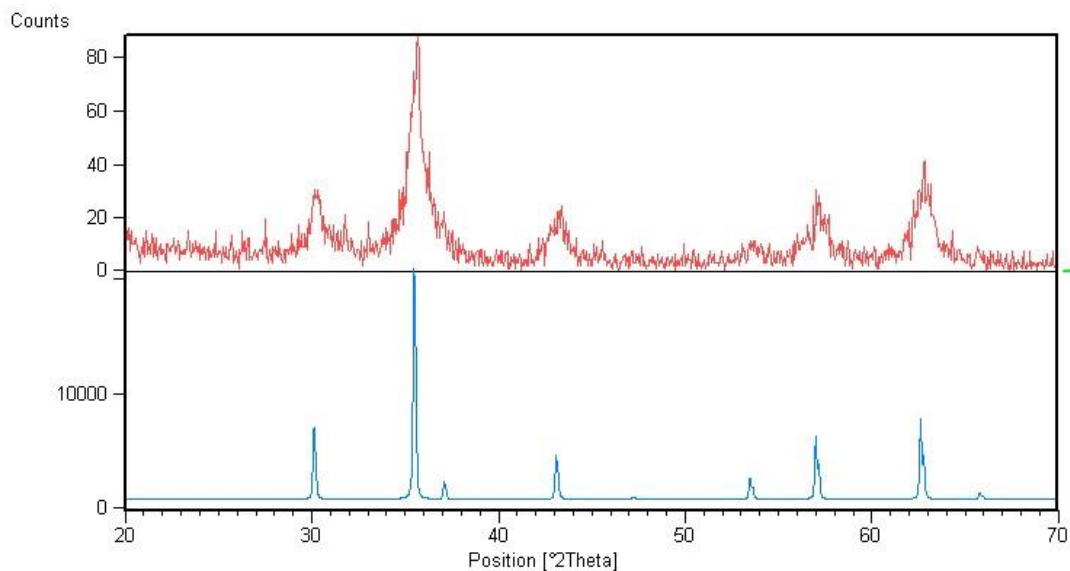


Figure 2. XRD pattern of synthesized CoFe_2O_4

Table 1. Peak analysis of XRD pattern of synthesized CoFe_2O_4

| 2θ (deg) | FWHM | Miller indices (hkl) |
|--------------------|--------|-------------------------|
| 30.22 | 0.3936 | 220 |
| 35.57 | 0.5904 | 311 |
| 43.14 | 0.9840 | 400 |
| 53.69 | 0.7872 | 422 |
| 57.22 | 0.7872 | 511 |
| 62.85 | 0.4920 | 440 |
| 74.32 | 0.7200 | 533 |

The sharp and broad peaks in this XRD pattern, confirming the single phase formation of pure CoFe_2O_4 with the expected cubic inverse spinel structure with $Fd\bar{3}m$ space group and without any impurity phase. The lattice

constant, calculated from (311) reflections were 8.3578.

The crystalline size of the particles was calculated using the modified Debye-Scherrer equations [31]. Modified Scherrer equation plots $\ln \beta$ against $\ln \frac{1}{\cos \theta}$ and obtains the intercept

of a least squares line regression. After getting the intercept, then the exponential of the intercept is obtained:

$$e^{\ln \frac{K\lambda}{L}} = \frac{K\lambda}{L} \quad (1)$$

Having $K = 0.9$ and λ ($\lambda_{\text{Cu}\alpha} = 0.15405 \text{ nm}$), from which a single value of L is obtained through all of the available peaks. The results indicate that nanocrystalline CoFe_2O_4 powder with crystallite size of 13 nm have been successfully obtained.

Photocatalytic activity

In this section, we report on the photoactivity of CoFe_2O_4 . Because of its environmental significance and nonbio-degradation, methyl orange was selected as a reliable model pollutant in photo catalytic activity investigation. The existence of an optimum hydrogen peroxide concentration is typical and well-known in photocatalytic oxidation. This optimum value was previously found to be 10 mM for MO degradation [32].

PH is another main factor influencing the rate of degradation of some organic compounds in the photo catalytic process. The photo degradation of MO at different pH from 3 to 10 have been studied [33,34], and the best results obtained in acidic solution (pH = 3).

The photo degradation of MO is carried out in the presence of CoFe_2O_4 photocatalyst and H_2O_2 under UV irradiation at pH=3. The results showed that the intensity of the characteristic peak of MO at $\lambda_{\text{max}} = 477 \text{ nm}$ decreased gradually and complete dis-coloration of dye was observed after 3 h under optimum conditions. This proves that photocatalytic degradation is a viable means of dye removal from wastewaters.

In the first step, calibration curve was obtained using standard MO solutions with known concentrations (Figure 3).

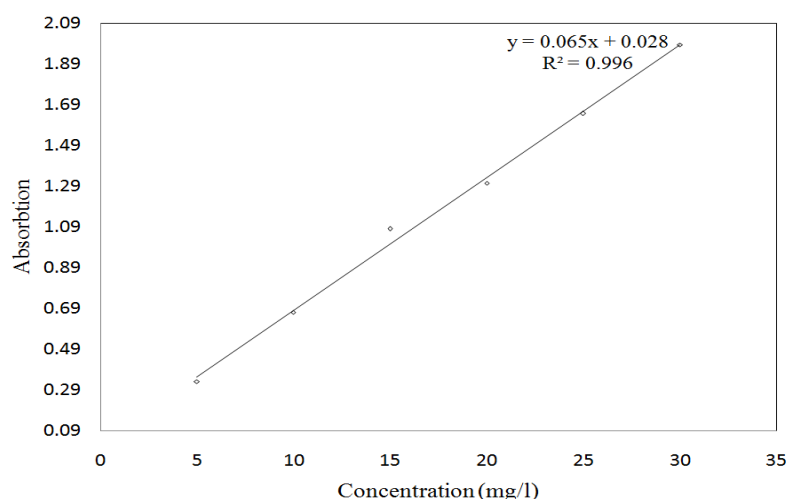


Figure 3. Calibration curve of MO

Consequently, the degradation efficiency of the photo catalytic process was evaluated by the degradation ratio (D) of MO, which was calculated with the following formula:

$$D(\%) = \frac{C_0 - C_t}{C_0} \times 100 \quad (2)$$

Where D% was the degradation rate of MO, C_0 and C_t denote the initial and the time-dependent concentration respectively. The results indicated that

CoFe₂O₄ exhibited the best efficiency for the degradation of MO under UV light irradiation, which the degradation ratio reached up to 100% after 3 h of irradiation. The attractive features of this degradation process were very short reaction time, high efficiency, simple work-up procedure, as well as provision of an ecofriendly and green synthesis making it an excellent alternative to other reported protocols [4-8].

Conclusion

CoFe₂O₄ nano magnetic particles were synthesized by a convenient, facile, reliable, cost effective and eco-friendly method in one pot reaction using Chenopodium album leaf extract. The crystalline size of magnetite nanoparticles was 13 nm and can be applied in a variety of existing applications. In this study, CoFe₂O₄ as photocatalyst showed a high activity for Methyl Orange degradation under UV irradiation. Magnetic nanoparticles have a good potential for treatment of contaminated water duo to easy separation by applying a magnetic field.

Acknowledgments

We are thankful to Payame Noor University for their support and encouragements.

References

- [1] X.Y. Song, Z.W. Qiu, X.P. Yang, H.B. Gong, S.H. Zheng, B.Q. Cao, H.Q. Wang, H. Mohwald, D. Shchukin, *Chem. Mater.*, **2014**, 26, 5113-5119.
- [2] D.V. Voronin, A.V. Sadovnikov, D.G. Shchukin, D.A. Gorin, E.N. Beginin, Y.P. Sharaevskii, S.A. Nikitov, *Tech. Phys. Lett.*, **2013**, 39, 715-718.
- [3] I. Sharifi, H. Shokrollahi, M.M. Doroodmand, R. Safi, *J. Magn. Magn. Mater.*, **2012**, 324, 1854-1861.
- [4] P.C. Rajath Varma, R.S. Manna, D. Banerjee, M. Raama Varma, K.G. Suresh, A.K. Nigam, *J. Alloy. Compounds.*, **2008**, 453, 298-303.
- [5] D.S. Mathew, R.S. Juang, *Journal of Chemical Engineering.*, 2007, 129(1-3), 51-65.
- [6] S.M. Daliya, R.S. Juang, *Chem. Eng. J.*, **2007**, 129, 51-65.
- [7] G.A. Elshobaky, A.M. Turkey, N.Y. Mostafa, S.K. Mohamed, *J. Alloy. Compd.*, **2010**, 439, 415-422.
- [8] E. Manova, D. Paneva, B. Kunev, C. Estournès, E. Rivière, K. Tenchev, A. Léaustic, I. Mitov, *J. Alloy. Compd.*, **2009**, 485, 356-361.
- [9] Q. Liu, J. Sun, H. Long, X. Sun, X. Zhong, Z. Xu, *Mater. Chem. Phys.*, **2008**, 108, 269-273.
- [10] S.D. Bhame, P.A. Joy, *Sens. Actuators A.*, **2007**, 137, 256-261.
- [11] I.H. Gul, A. Maqsood, *J. Alloy. Compd.*, **2008**, 465, 227-231.
- [12] H.A. Salam, P. Rajiv, M. Kamaraj, P. Jagadeeswaran, S. Gunalan, R. Sivaraj, *Int. J. Biol. Sci.*, **2012**, 1, 85-90.
- [13] M. Mahdavi, F. Namvar, M.B. Ahmad, R. Mohamad, *Molecules*, **2013**, 18, 5954-5964.
- [14] J. Kasthuri, S. Veerapandian, N. Rajendiran, *Colloids Surf. B*, **2009**, 68, 55-60.
- [15] A.M. Awwad, N.M. Salem, *J. Nanosci. Nanotechnol.*, 2012, 2, 208-213.
- [16] M.G. Moghaddam, R. Hadi-Dabanlou, M. Khajeh, M. Rakhshanipour, K. Shameli, *Korean. J. Chem. Eng.*, **2014**, 31, 548-557.
- [17] S.P. Dubey, M. Lahtinen, M. Sillanpää, *Process Biochem.*, **2010**, 45, 1065-1071.
- [18] N.C. Sharma, S.V. Sahi, S. Nath, J.G. Parsons, J.L. Gardea-Torresdey, T. Pal, *Environ. Sci. Technol.*, **2007**, 41, 5137-5142.

- [19] H. Bar, D.K. Bhui, G.P. Sahoo, P. Sarkar, S. Pyne, A. Misra, *Colloids Surf. A.*, **2009**, *348*, 212–216.
- [20] R. Pasricha, A. Singh, M. Sastry, *J. Colloid Interface Sci.*, **2009**, *333*, 380–388.
- [21] M. DellaGreca, C.D. Mariono, A. Zarrelli, B.D. Abrosca, *J. Nat. Prod.*, **2004**, *67*, 1492–1495.
- [22] M. Dellagrecia, L. Previtiera, A. Zarrelli, *Nat. Prod. Res.*, **2005**, *19*, 87–90.
- [23] F. Cutillo, B. Abrosca, M. Dellagrecia, C.D. Marino, A. Golino, L. Previtiera, A. Zarrellia, *Phytochemistry.*, **2003**, *64*, 381–1387.
- [24] A. Monshi, M.R. Foroughi, M.R. Monshi, *World J. Nano Sci. Eng.*, **2012**, *2*, 154–160.
- [25] Y. Li, F.S. Zhang, *Chem. Eng. J.*, **2010**, *158*, 148–153.
- [26] N. Bao, X. Feng, Z. Yang, L. Shen, X. Lu, *Environ. Sci. Technol.*, **2004**, *38*, 2729–2736.
- [27] W. Nam, J. Kim, G. Han, *Chemosphere.*, **2002**, *47*, 1019–1024.
- [28] F. Cutillo, B. Abrosca, M. Dellagrecia, C.D. Marino, A. Golino, L. Previtiera, A. Zarrellia, *Phytochemistry*, **2003**, *64*, 381–387.
- [29] A. Monshi, M.R. Foroughi, M.R. Monshi, *World J. Nano Sci. Eng.*, **2012**, *2*, 154–160.
- [30] Y. Li, F.S. Zhang, *Chem. Eng. J.*, **2010**, *158*, 148–153.
- [31] N. Bao, X. Feng, Z. Yang, L. Shen, X. Lu, *Environ. Sci. Technol.*, **2004**, *38*, 2729–2736.
- [32] W. Nam, J. Kim, G. Han, *Chemosphere*, **2002**, *47*, 1019–1024.